

“AN EXPERIMENTAL INVESTIGATION ON PROPERTIES OF CONCRETE WITH FOUNDRY SAND AND GLASS FIBER”

Abhishekh Soratur¹, Ajay B K², Soumya P Hiremath³, Tejashwini P Maganur⁴, Rajesh S J⁵

^{1,2,3,4} Student, Department of civil Engineering, S T J Institute of Technology, Ranebennur, Karnataka, India

⁵ Assistant Professor, Department of civil Engineering, S T J Institute of Technology, Ranebennur, Karnataka, India

Abstract - Fiber reinforced concrete used widely for its better performance in aggressive environment. Addition of Glass fibre is increasing confinement and arresting cracks in plain and reinforced concrete. In this work presents experimental studies on Glass fibre reinforced concrete made with used foundry sand as partial replacement of fine aggregate. To evaluate the mechanical properties of the concrete mixes, Specimens were tested by Compression, split-tensile and flexural strength. Test results were indicated a marginal increase in the mechanical properties of plain and Glass fiber reinforced concrete by the inclusion of foundry sand as a partial replacement of fine aggregate. Utilization of foundry sand in various engineering applications can solve the waste management problem in disposal of foundry sand and other issues.

Keywords: Glass fibre, used foundry sand, Partial replacement, Compressive strength, split tensile strength, flexural strength.

1. INTRODUCTION

Concrete is most widely used construction material in the world. Now days the world is witnessing the construction of more and more challenging and difficult Engineering structures. So, the concrete need to possess very high strength and sufficient workability. Researchers all over the world are developing high performance concrete by adding various fibres, admixtures in different proportions. Various fibres like glass, carbon, Polypropylene and aramid fibres provide improvement in concrete properties like tensile strength, fatigue characteristic, durability, shrinkage, impact, corrosion resistance and serviceability of concrete. Because of such characteristics fibre Reinforced Concrete has found many applications in civil engineering field. The inclusion of fibers in concrete slabs has showed satisfactory performance with improved mechanical properties and reduced early age micro cracking. Classifications of foundry sand mainly depend upon the type of binder and binder system used in metal casting. Some of the foundry sand which is use for metal casting is green sand and chemically bonded sand. Resin coated sand, cold box sand, hot box sand; CO₂ sands are some common type of chemically bonded sand. (Mould and core test handbook,

American Foundry Society ISBN-087433-228-1). Indian foundries deliver roughly 1.71MT of waste foundry sand (WFS) in every year. Foundry sand is high quality silica sand with uniform physical characteristics. It is a by-product of ferrous and nonferrous metal casting industries, where sand

has been used for centuries as a moulding material because of its thermal conductivity. Foundries successfully recycle and reuse the sand many times in a foundry. When the sand can no longer be reused in the foundry, it is removed from the foundry and is termed foundry sand. The physical and chemical characteristics of foundry sand depend on the type of casting process and the industry sector from which it originates. In modern foundry practice, sand is typically recycled and reused through many production cycles.

1.1 OBJECTIVES

- To study the compressive, flexural strength impact of M20 concrete.
- To study the compressive strength of concrete by adding foundry sand and glass fiber
- To study the split tensile of concrete by adding foundry sand and glass fiber
- To study the flexural strength of concrete by adding foundry sand and glass fiber

2. METHOD & MATERIAL

2.1 MATERIALS

The cement used was Ordinary Portland Cement 53 grade. It was tested as per the Indian Standard Specifications BIS: 12269-1987. Properties of the cement are tested according to IS given in Table 1. Waste foundry sand was obtained from a Metal casting industry, Madurai. Fine aggregate was natural sand having a 4.75 mm nominal size and conforming zone II. The coarse aggregate used in this investigation was 12.5 mm nominal size. Both aggregates and waste foundry sand were tested according to BIS: 383-1970. A thin and short fibre will only be effective the first hours after pouring the concrete. Their physical properties are given below.

Table 1: Properties of Cement

SL. NO	PROPERTY	VALUES OBTAINED
1	Compressive strength	53MPa
2	Specific gravity	3.15
3	Standard consistency	31%
4	Initial setting time	30Min
5	Final setting time	370 Min

Table 2: Properties of Fine and Coarse Aggregate

SL.NO	PROPERTIES	FA	UFS	CA
1	Size	4.75	4.75	12.5
2	Bulk density	1721	1524	1650
3	Fineness modulus	2.8	2.21	6.8
4	Specific gravity	2.55	1.85	2.70

Table 3: Properties of Glass Fibre

SL NO	PROPERTIES	VALUES
1	Type	E Glass fiber
2	Length	6mm
3	Tensile strength	3.5Gpa
4	Modulus	73.5Gpa
5	Density	2720m3

2.2 MIXTURE PROPORTIONS

Four concrete mixture proportions were made. First was the control mix (without UFS) and the other three mixtures contained UFS. Fine aggregate (regular sand) was replaced with UFS by weight. The FS used in this study was washed by fresh water more than four times to remove ash and clay particles. The proportions of fine aggregate replaced were 10%, 20% and 30%. The control mixture without UFS was proportioned as per the Indian Standard 10262-2007 to have a 28 day cube compressive strength of 37.53 MPa. Concrete mixes were made in power driven revolving-type drum mixers of capacity 1 m3.

3. RESULTS & DISCUSSIONS

3.1 COMPRESSIVE STRENGTH

150 mm concrete cubes were cast using with w/c ratio of 0.5. Specimens were prepared with OPC (control) and fine aggregate replaced by foundry sand at various percentages like 10%, 20% and 30% and also adding 0.5% of glass fibre. During moulding, the cubes were mechanically vibrated. After 24 hours, the Specimens were removed from the mould and subjected to water curing for 28 days. After curing, the specimens were tested for compressive strength using a compression testing machine (CTM) having capacity 2000 KN. The concrete cubes were tested accordance with the IS standards at the 7, 14 and 28 days. Concrete mixtures containing Glass fibre and Foundry sand shows higher strength than control mix. Compressive strength results are shown below. in the fig 1 At the age of 28 days strength was increased. In Fig 1, it is found that increasing replacement percentage of UFS shows gradual increasing of compressive strength when compared to control mix.

Table 4: Average Compressive and Splitting tensile Strength in MPa at various ages

Mix Designation	Compressive Strength			Splitting Tensile Strength		
	7 Days	14 Days	28 Days	7 Days	14 Days	28 Days
M1	27.31	33.74	36.53	0.93	1.43	1.82
M2	30.34	36.32	39.28	1.02	1.64	2.13
M3	33.65	38.44	42.64	1.37	1.61	2.35
M4	35.24	39.53	46.72	1.63	2.14	2.52

Fig 1: Compressive Strength of Concrete at 28 Days

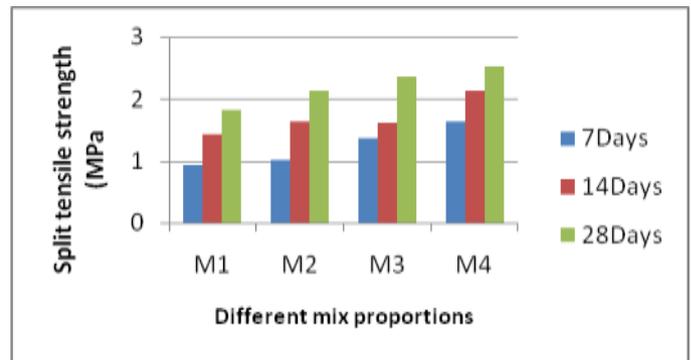
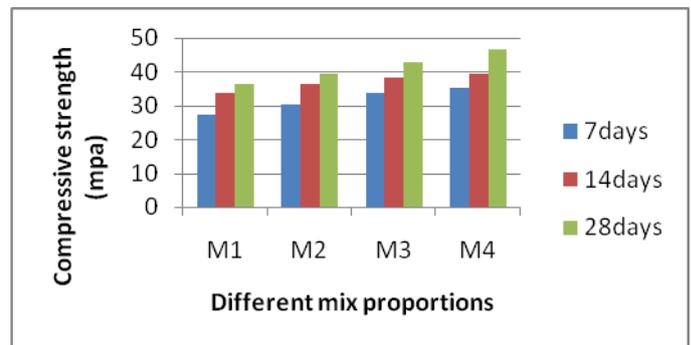


Fig 2: Split tensile Strength of Concrete at 28 Days

3.2 SPLIT TENSILE STRENGTH

Standard cylinder moulds of size (100mm x 300mm) were cast for split tensile strength. In this test compressive line loads were applied along a vertical symmetrical plane, which causes splitting of specimen. The tests were carried out on three specimens and average split-tensile strength values were obtained as per BIS: 5816-1999. The splitting tensile strength of concrete mixtures was found out at the age of 28 days. The results of splitting tensile strength are shown. Increase in UFS content led to an increase in splitting tensile strength when compared to Control Mix. The percentage increase in strength at 28 days. In this test showed better results when compared with Control Concrete mix.

3.3 FLEXURAL STRENGTH TEST FOR PCC AND RCC BEAMS

3.3.1 FLEXURAL STRENGTH FOR PCC BEAMS

The specimens were tested under two point loading. Standard beam moulds of size 100 mm x 100 mm x 500 mm were cast for the preparation of concrete specimens for flexural strength. A table vibrator was used for compaction of hand filled concrete beams. The specimens were demoulded after 24 hours and subsequently immersed in water for 28 days. For each age three specimens were used for the determination of average flexural strength. The Flexural strength of the concrete measured at the age of 28 days and the strength values are listed. Flexural strength of concrete mixtures increased with the increase in foundry sand content by adding glass fibre. The flexural strength was increased.

3.3.2 TWO POINT LOAD SETUP FOR RCC BEAMS

Two point loading system was adopted for the tests. The beams were mounted over two pedestals and the concentrated loads were applied by means of 40 Tonnes Universal Testing machine (UTM). Deflections measured by using linear voltage displacement transducers (LVDTs) and were kept at mid-span as well under the loading points. The load at which the concrete has started to rupture, the failure load of the specimens and also the nature of failure modes were noted for each beam.

The ultimate load carrying capacity of the R.C.C beams under flexural loading is relatively increased with increasing the various percentages of R.C.C members. The flexural strength of beam is calculated by the equation, Flexural strength (N/mm² or MPa) = (P x L) / (b x d²), Where, P = Failure load, L = Centre to center distance between the support = 1500 mm b = width of specimen=100 mm d = depth of specimen= 150 mm Figure 5 shows the comparison of the load deflection behavior of various percentages of foundry sand in R.C.C R.C.C beams. It can be understand that the ultimate load was increased by replacing various percentages of foundry sand. The flexural strength of RCC beams was increased up to 15.3%, 24.94% and 33.17% when compared to Concrete mix. Their results of flexural strength for RCC and PCC beams are shown in Table 6.

Table 5: Average flexural strength (N/mm²) at 28 days

MIX DESIGNATION	7 DAYS	14 DAYS	28 DAYS
M1	10.4	11.2	12.00
M2	9.6	10.4	11.6
M3	10.8	11.6	12.4
M4	11.6	12.2	13.4

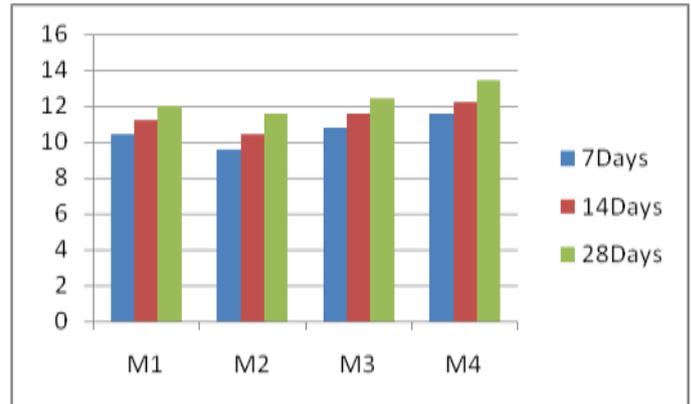


Figure 3: Flexural strength for R.C.C beams

4. CONCLUSION

1. Compressive strength, splitting-tensile strength and flexural strength test results of concrete mixtures was increased with foundry sand and glass fibre.
2. At the age of 28 days sand content is replaced by foundry sand and addition fibers shows compressive, Spilt tensile, flexural strength was increased.
3. Waste foundry sand can be successfully used in making great quality ready-mix concrete as partial Supplanting of fine aggregate.
4. Environmental effects from wastes and disposal problems of waste can be reduced through this research
5. A better measure by an innovative Construction Material is formed through this research.

REFERENCES

1. N Í. Navarro-Blasco, J.M. Fernández, A. Duran, R. Sirera, J.I. Álvarez "A novel use of calcium aluminate cements for recycling waste foundry sand (WFS)" Construction and Building Materials, Volume No. 28, pp. 218–228, 2013.
2. G. Ganesh Prabhu, Jung Hwan Hyun, Yun Yong Kim "Effects of foundry sand as a fine aggregate in concrete production", Construction and Building Materials, Volume No. 70, pp. 514–521, 2014.
3. Gurpreet Singh and Rafat Siddique "Abrasion resistance and strength properties of concrete containing waste foundry sand (WFS)", Construction and Building Materials, Vol. 28, pg. 421–426, (2012).
4. J Gurdeep Kaur, and Rafat Siddique, Anita Rajor " Properties of concrete containing fungal treated waste foundry sand ", Construction and Building Materials, Vol.29, (2012) 82-87.

5. Mehran Khan, Majid Ali "Use of glass and nylon fibers in concrete for controlling early age micro cracking in bridge decks" Construction and Building Materials, Volume No .125, pp.800-808, 2016
6. Shrikant M. Harle "Review on the Performance of Glass Fiber Reinforced Concrete" International Journal of Civil Engineering Research, ISSN 2278-3652 Volume 5, Number 3 (2014), pp. 281-284
7. Deshmukh S.H., Bhusari J.P., Zende A.M. (2012) "Effect of glass fibres on ordinary Portland cement concrete," IOSR Journal of Engineering June. 2012, Vol. 2(6), ISSN: 2250-3021, pp: 1308-1312.
8. Rafat Siddique, Geert de Schutter , Albert Noumowe "Effect of used-foundry sand on the mechanical properties of concrete" Construction and Building Materials, 23 (2009) 976-980
9. BIS: 12269-1987, Specifications for 53-Grade Portland cement, Bureau of Indian Standards, New Delhi, India.
10. BIS: 383-1970, Specifications for coarse and fine aggregates from natural sources for concrete, Bureau of Indian Standards, New Delhi, India.
11. BIS: 10262-2009, recommended guidelines for concrete mix design, Bureau of Indian Standards, New Delhi, India.
12. BIS: 5816-1999. Indian standard code of practice-splitting tensile strength of concrete-method of test, Bureau of Indian Standards, New Delhi, India.